

ROMA USA LLC
554 North Avenue NW, Suite B
Atlanta, GA 30318
USA

Eurofins Product Testing A/S
Smedeskovvej 38
8464 Galten
Denmark

voc@eurofins.com
www.eurofins.com/voc-testing

Date
17 March 2015


VOC Emission Test report

1. Sample Information

Sample identification	ECODOMUS SATIN BASE TR
Product type	Paint
Batch no.	250/914B
Production date	13-11-2014
Date when sample was received	21/01/2015
Testing (start - end)	10/02/2015 - 10/03/2015

2. Resulting VOC Emission Class Label

This recommendation is based on French regulation of March 23, 2011 (décret DEVL1101903D) and of April 19, 2011 (arrêté DEVL1104875A). For details please see www.eurofins.com/france-voc

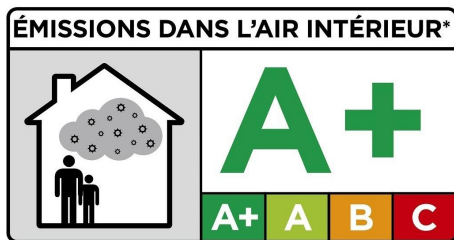

*Information sur le niveau d'émission de substances volatiles dans l'air intérieur, présentant un risque de toxicité par inhalation, sur une échelle de classe allant de A+ (très faibles émissions) à C (fortes émissions).

The product was assigned a VOC emission class without taking into account the measurement uncertainty associated with the result. As specified in French Decree no. 2011-321 of March 23, 2011, correct assignment of the VOC emission class is the sole responsibility of the party responsible for distribution of the product in the French market.

3. Test Method

Method	Principle	Parameter	Quantification limit	Uncertainty	
ISO 16000 parts -3, -6, -9, -11 Internal method numbers: 9810, 9811, 9812, 2808B, 8400	GC/MS HPLC/UV	VOC Volatile aldehydes	2 µg/m ³ 3 µg/m ³	22% (RSD) Um = 2 x RSD= 45 %	
Test chamber parameter					
Chamber volume, l	119	Temperature, °C	23±1	Relative humidity, %	50±3
Air change rate, 1/h	0.5	Loading ratio, m ² /m ³	1		
Test condition: Sample stayed in test chamber during the whole 28 days testing period.					
Sample preparation					
The sample was homogenised and applied onto a glass plate.					
Layer	Application amount, g/m ²	Mixing ratio, paint : water	Drying time, h		
1	78	5.25 : 1	1		
2	78	5.25 : 1	16		
3	78	5.25 : 1	-		

4. Results

	Concentration after 28 days $\mu\text{g}/\text{m}^3$	C	B	A	A+
TVOC	< 2	>2000	<2000	<1500	<1000
Formaldehyde	< 3	>120	<120	<60	<10
Acetaldehyde	< 3	>400	<400	<300	<200
Toluene	< 2	>600	<600	<450	<300
Tetrachloroethylene	< 2	>500	<500	<350	<250
Ethylbenzene	< 2	>1500	<1500	<1000	<750
Xylene	< 2	>400	<400	<300	<200
Styrene	< 2	>500	<500	<350	<250
2-Butoxyethanol	< 2	>2000	<2000	<1500	<1000
1,2,4-Trimethylbenzene	< 2	>2000	<2000	<1500	<1000
1,4-Dichlorobenzene	< 2	>120	<120	<90	<60

< Means less than
> Means higher than



Maria Pelle
Chemist